

SMALL ANGLE X-RAY SCATTERING TECHNIQUE IN STUDYING THE MORPHOLOGICAL STRUCTURE OF THERMOPLASTIC NATURAL RUBBER

Abdul Aziz Mohamed¹, Hafizal Yazid² and Megat Harun M. A.²

¹ Centre for Nuclear Energy, College of Engineering, Universiti Tenaga Nasional, 43000 Kajang, Selangor, Malaysia.

² Materials Technology Group, Malaysian Nuclear Agency, Bangi, 43000 Kajang, Selangor, Malaysia.

e-mail: azizm@uniten.edu.my

ABSTRACT

Thermoplastic natural rubber sample is found isotropic based on Small Angle X-Ray Scattering (SAXS) pattern. Morphological interpretation was deduced based on ideal lamellar morphology using 1-D correlation function. The fitting was carried out using Porod tail model and Vonk for back-extrapolated model. It is found that the long period value is 15.7nm which is comparable to results obtained from Lorentz corrected profile, 20nm. Crystalline thickness and amorphous thickness was found as 13.4 and 2.31nm respectively.

ABSTRAK

Sampel getah asli termoplastik didapati isotropik berdasarkan Sudut Kecil Serakan Sinar-X (SAXS) yang corak pencirian morfologi telah diperolehi berdasarkan model morfologi lamela unggul menggunakan 1-D fungsi korelasi. Penjajaran data dibuat menggunakan model ekor Porod dan Vonk untuk model back-diekstrapolasi. Ia didapati bahawa nilai berkala yang panjang adalah 15.7nm yang setanding dengan keputusan yang diperolehi daripada Lorentz diperbetulkan profil, 20nm. ketebalan kristal dan ketebalan amorfus ditemui kerana masing-masing 13.4 dan 2.31nm.

Keywords: small angle scattering, natural rubber, lamellar morphology, x-ray

INTRODUCTION

Structural parameters such as long spacing, amorphous and crystal length of a sample could be derived from SAXS data by using a correlation function analysis [1, 2]. The correlation function is simply the Fourier Transform of the SAXS curve which is related to the electron density distribution within the sample. The structural parameters are obtained by interpretation of the 1-D correlation function. The interpretation assumes that the sample has an ideal lamellar morphology [3]. The morphology consists of an ensemble of isotropically distributed stacks of alternating crystalline and amorphous lamellae. The stacks are assumed to be of dimensions that are large enough not to affect the small angle scattering.

There are three stages involved in the correlation function analysis:

- i. Extrapolation of the data to $q = 0$ and $q = \infty$.

ii. Calculation of the Fourier transform of the extrapolated data.

iii. Interpretation of step ii.

The SAXS data must first be extrapolated to $q = 0$ and $q = \infty$ prior to calculating the Fourier transform to avoid the introduction of series termination errors in the transform. Extrapolation to $q = \infty$ is performed by fitting either a Porod [4] or Sigmoid [5] function to the tail of the SAXS data. The tail-fit affects the correlation function in the most important region for the extraction of ideal lamellar morphology parameters. The typical tail fitting functions used are given as:

$$I(q) = B + \frac{K}{q^4} \quad \text{Porod} \quad (1)$$

$$I(q) = B + \frac{K}{q^4} e^{-q^2 \theta^2} \quad \text{Sigmoid} \quad (2)$$

where,

B = Bonart thermal background.

K = Porod constant

The data are extrapolated to $q = 0$ by fitting a Guinier or Vonk model to the first few genuine data points after the beam stopper position. If the experimental data do not increase in intensity as the beam stopper region is approached, back-extrapolation may fail. Fitting functions for back-extrapolation are given as:

$$I(q) = A e^{Bq^2} \quad \text{Guinier} \quad (3)$$

where,

A = form factor constant

$$I(q) = H_1 - H_2 q^2 \quad \text{Vonk} \quad (4)$$

where,

H_1 and H_2 = Lorentz constants.

The original SAXS data and tail-fit are joint and smoothed by applying the Savitzky-Golay [6] smoothing algorithm. This approach smooths the data without greatly altering higher moments. It is also avoided the formation of ripples in the correlation function that would occur with a period matching the d-spacing of the join. No smoothing is used at the join of the back-extrapolation to the SAXS data.

EXPERIMENTAL WORK

SAXS experiments were performed using the Hecus SWAX instrument, Malaysian Nuclear Agency, operated at 50kV and 1mA with the point collimation geometry. The radiation used was a Ni filtered CuK α radiation of

wavelength 0.154nm (Seifert, Ahrensburg, Germany). The intensity profiles are recorded using a 2-D detector (Pilatus) and the scattering vector q , covers from 0.01 to 0.6 \AA^{-1} . One-dimensional scans of $I(q)$ were extracted from two- dimensional scattering patterns using the analysis package Fit2D [7]. Angular calibration of the scattered intensities in the small angle regime for the detector is performed using silver stearate ($d = 48.68 \text{\AA}$). Sample to detector distance is 271mm and sample exposure to the source is 600 seconds. All experiments are carried out at room temperature, 20 °C. Validation experiment is carried out using a reference material, alumina type 150 (Al_2O_3) CRM BAM-PM-104.

Sample of polymer blend consists of 50% natural rubber (Nr), 10% liquid natural rubber (Lnr) and 40% high density polyethylene (HDPE). Nr (SMR L grade) was supplied by Malaysian rubber research institute, RRI (Malaysia). The density of Nr is 0.95g/cm³. HDPE was supplied by Titan Chemicals Corp. Bhd. (Malaysia) with a density of 0.91g/cm³. Lnr was produced from Nr with weight average molecular weight relative to polystyrene as $M_w = 40 \times 10^4$.

RESULT AND DISCUSSIONS

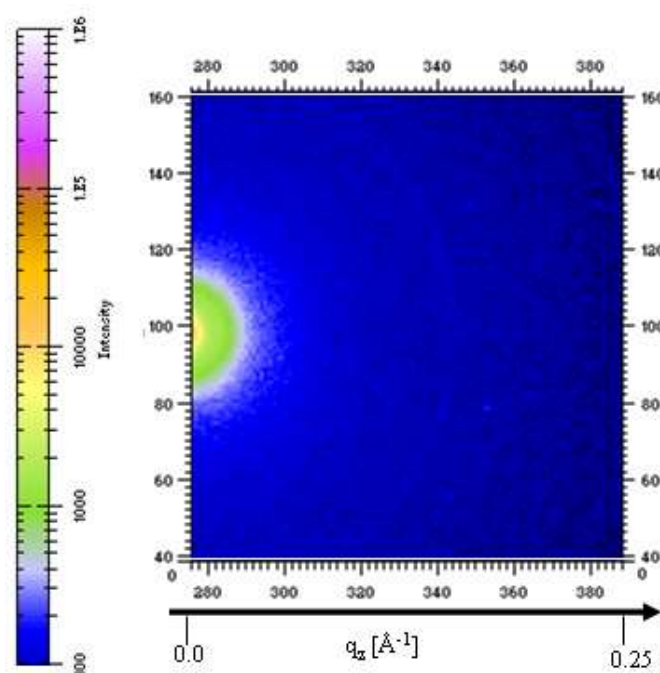


Figure 1: 2-D SAXS profile (Courtesy Dr Hafizal, Nuklear Malaysia)

Based on Figure 1, there is no preferred orientation of the structure within the plane of the samples. This proves that the sample is fully isotropic. However, this does not exclude the possibility that a preferred nematic type orientation exist perpendicular to the surface. Rings at larger angles are due to Be window.

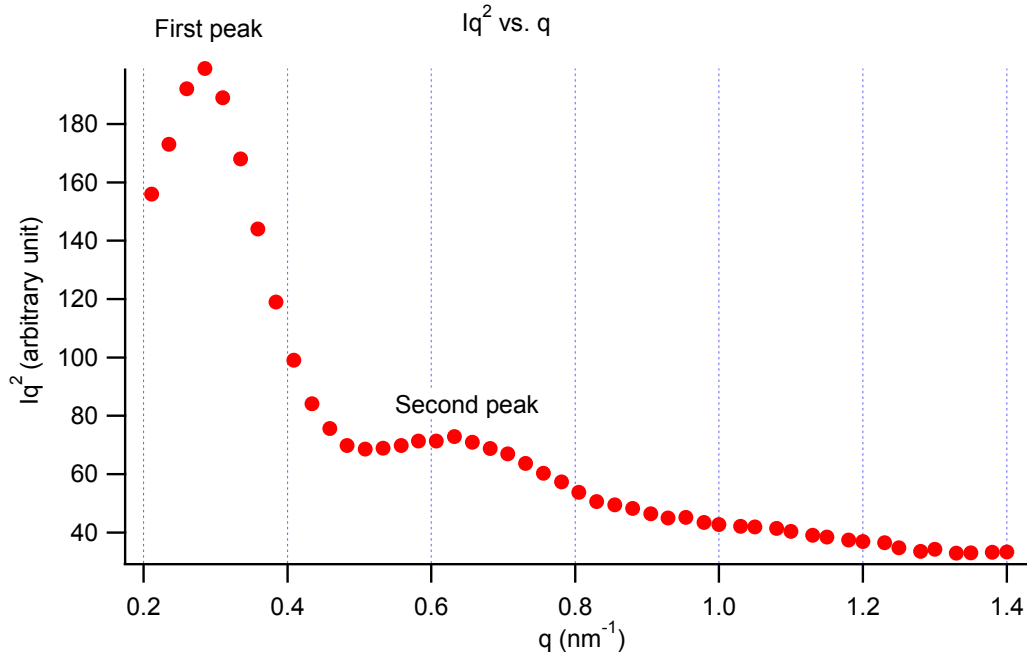


Figure 2: Lorentz-corrected SAXS profile for compatibilized TPNR blend

Figure 2 shows the Lorentz-corrected SAXS profile for compatibilized 60/40 NR/HDPE blend. In this figure, the Iq^2 (arbitrary unit) is plotted against the scattering vector q where;

$$q = \frac{4\pi}{\lambda} \sin \theta \quad (5)$$

where,

θ is scattering angle;

λ is the incident wavelength.

It is observed that there are scattering peaks at $q = 0.3$ and 0.6 nm^{-1} caused by the inter-lamella interference from the lamella crystal structures in the HDPE domains. The peak corresponds to the first and second order peaks and from that the lamella spacing l_s is calculated. In this work, the lamella spacing or long spacing is ca. 20 nm. This is in agreement with the previous result which is also ca. 20 nm [8].

Morphological parameter is extracted from Fig. 3. It is found that long spacing is 15.7nm. Crystalline thickness and amorphous thickness was found to be 13.4 and 2.31nm respectively.

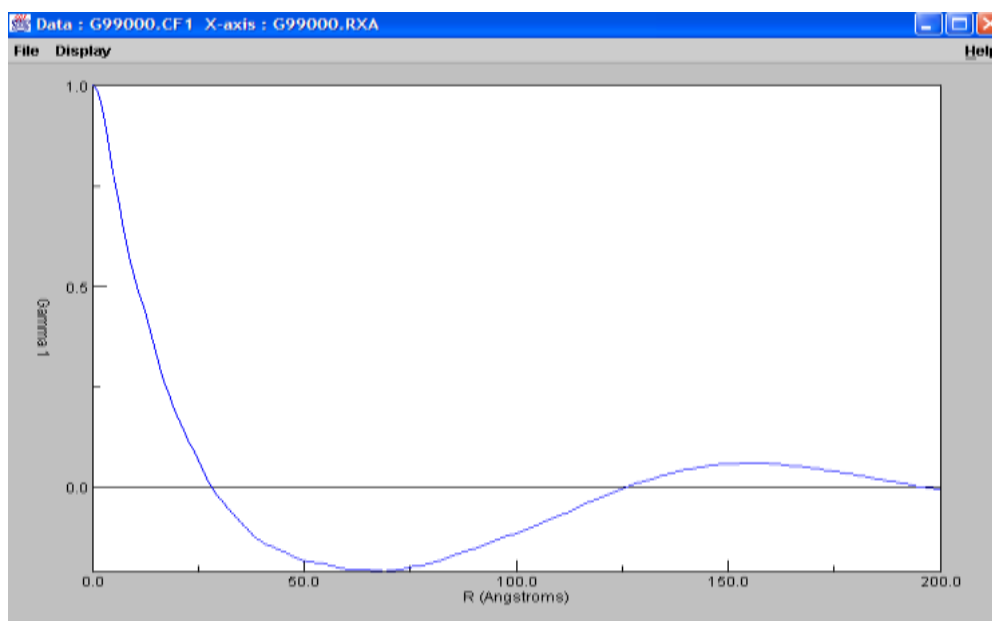


Figure 3: Result of correlation function

CONCLUSION

The technique of using correlation function to probe morphological parameter is found to be promising and comparable with other technique. In this work, three parameters were successfully investigated namely long spacing, crystalline thickness and amorphous thickness.

ACKNOWLEDGMENT

The authors would like to thank to Malaysian Nuclear Agency for supporting this study. Thank also goes to Materials Technology group of the agency for running the experiment using the SAX instrument available in the agency.

REFERENCES

- [1] Strobl, G. R. and Schneider, M. J., Polym. Sci. (1980) 18, 1343-1359.
- [2] Balta Calleja, F.J. and Vonk, C. G., X-ray Scattering of Synthetic Polymers, Elsevier Amsterdam 1989, 247-257.
- [3] Glatter, O. and Kratky, O., Small Angle X-ray Scattering, Academic Press Inc. London Ltd. 1982, 433-466
- [4] Balta Calleja, F.J. and Vonk, C. G., X-ray Scattering of Synthetic Polymers, Elsevier Amsterdam 1989, 257-261.
- [5] Koberstein, J. and Stein R. J., Polym. Sci. Phys. Ed. (1983) 21, 2181-2200.
- [6] Press, W. H. et. al., Numerical Recipes: the Art of Scientific Computing, Cambridge University Press 1986.
- [7] Hammersley, A. P., ESRF. <http://www.esrf.fr/computing/scientific/FIT2D> (accessed June 2010).
- [8] Kazuhiro et. al., Composites: Part A 36 (2005) 423-429.